

Mixing Thermodynamics and Photocatalytic Properties of GaP–ZnS solid solutions

Joel Shenoy, Judy N. Hart, Ricardo Grau-Crespo, Neil L. Allan, and Claudio Cazorla*

Preparation of solid solutions represents an effective means to improve the photocatalytic properties of semiconductor-based materials. Nevertheless, the effects of site-occupancy disorder on the functional properties of materials are difficult to predict and consequently many experimental trials may be required before achieving enhanced photocatalytic activity. Here, first-principles methods are employed to estimate the mixing free energy and the structural and electronic properties of $(\text{GaP})_x (\text{ZnS})_{1-x}$ solid solutions. The method relies on a multi-configurational supercell approach that takes into account the configurational and vibrational contributions to the free energy. Phase competition among the zinc-blende and wurtzite polymorphs is also considered. Overall excellent agreement with the available experimental data is demonstrated, namely: 1) zinc-blende is energetically most favorable, 2) the solid solution energy band gap lies within the 2–3 eV range, and 3) the energy band gap of the solid solution is direct for compositions $x \leq 75\%$. It is found that at ambient conditions, $(\text{GaP})_x (\text{ZnS})_{1-x}$ solid solutions with $x \approx 25\%$, 50% and 75% render promising hydrogen evolution photocatalysts for water splitting under visible light, owing to their favorable energy band gaps and band levels relative to vacuum.

1. Introduction

Storing solar energy is critical for promoting the on-demand use of renewable energy sources. A promising solar-energy storage approach consists of generating hydrogen fuel by photocatalytic water splitting under sunlight.^[1–3] For this scheme to progress, it is necessary to find inexpensive and efficient photocatalytic materials. Binary semiconductors, such as TiO_2 , ZnS, and ZnO, have received great attention in this context owing to their natural

J. Shenoy, Dr. J. N. Hart, Dr. C. Cazorla
School of Materials Science and Engineering
UNSW
Sydney, NSW 2052, Australia
E-mail: ccazorla@icmab.es; c.cazorla@unsw.edu.au

Dr. R. Grau-Crespo
Department of Chemistry
University of Reading
Reading RG6 6AD, UK

Prof. N. L. Allan
School of Chemistry
University of Bristol
Cantock's Close, Bristol BS8 1TS, UK

 The ORCID identification number(s) for the author(s) of this article can be found under <https://doi.org/10.1002/adts.201800146>

DOI: 10.1002/adts.201800146

abundance, structural simplicity, and scalable synthesis. While a direct band gap of around 2–3 eV is most desirable for photocatalytic applications,^[1–3] binary semiconductors usually present wide and/or indirect energy band gaps that limit their absorption of visible light.

Solid solutions have emerged as an effective means to improve the photocatalytic performance of binary semiconductors. The main idea consists of mixing isostructural compounds with complementary electronic properties (e.g., a wide and direct energy band gap semiconductor with a narrow and indirect energy band gap semiconductor) in order to breed new materials with improved photocatalytic performance. Examples of solid-solution photocatalysts include $(\text{CdS})_x (\text{ZnS})_{1-x}$,^[4] $(\text{GaN})_x (\text{ZnO})_{1-x}$,^[5] $(\text{LaCoO}_3)_x (\text{NaTaO}_3)_{1-x}$,^[6] and $\text{In}_{1-x}\text{Ni}_x\text{TaO}_4$.^[7]

Nevertheless, the effects of site-occupancy disorder, that is, nonperiodic occupation of lattice sites in a crystal, on the electronic properties of solid solutions are challenging to foresee; consequently, many experimental attempts may be required before achieving any photocatalytic enhancement. In addition, inhomogeneity in the synthesized materials, caused by poor thermal stability of the compound mixtures, may limit performance. In this regard, computer simulations are useful since insightful analysis of the thermodynamic, structural, and electronic properties of photocatalytic materials can be performed in a systematic and cost-effective manner.^[8–10] Nevertheless, the nonperiodic occupancy of lattice sites makes modeling of solid solutions challenging.^[11–14]

Several theoretical methods have been introduced in the literature to simulate solid solutions, which can be classified into three main categories. The first group involves approaches in which a sort of “average” atom is defined to recover the perfect periodicity of the system, which is beneficial from a computational point of view. In the context of first-principles calculations, this can be achieved via the virtual-crystal approximation, in which the potential felt by the electrons is obtained by averaging over multiple atoms.^[15] In the second category of methods, the effects of site-occupancy disorder are straightforwardly reproduced by randomly occupying the lattice sites in a large periodic supercell.^[16,17] Since the involved supercell has to be large enough to mimic a random solution, this approach may be computationally very intensive. A special cell generation technique was introduced by

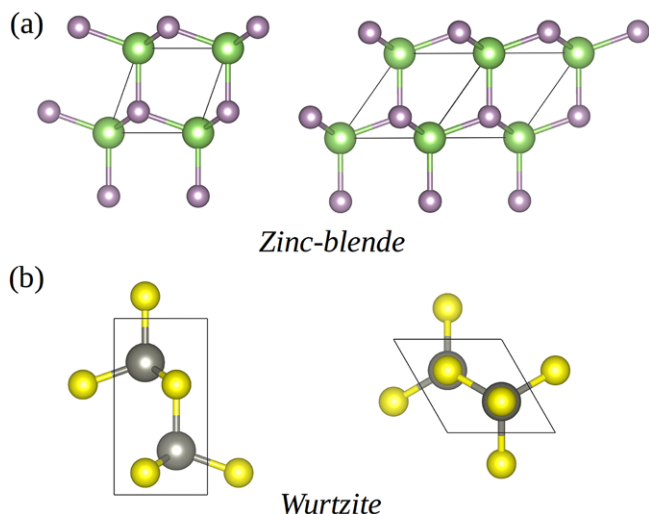


Figure 1. Polymorphism of bulk GaP and ZnS. a) The zinc-blende structure with space group $F\bar{4}3m$ and cubic symmetry. b) The wurtzite structure with space group $P6_3mc$ and hexagonal symmetry. Ga and Zn atoms are represented with green and black spheres and P and S atoms with purple and yellow spheres, respectively. In both structures, the ions are fourfold coordinated.

Zunger et al.^[18] to construct quasi-random simulation supercells that are approachable with first-principles methods. The third type of solid-solution simulation method is typified by the multi-configurational supercell approach,^[19,20] in which the entire configurational space of a disordered system is first generated (for a finite-size supercell) and subsequently reduced to a manageable set of inequivalent configurations by exploiting symmetry relations. Each inequivalent configuration is ascribed a Boltzmann-like occurrence probability that depends on its energy and configurational degeneracy, thus allowing for a full statistical treatment of the thermodynamic and functional properties of the material.

In this work, we present a comprehensive first-principles study of the mixing stability, and structural and electronic properties of $(\text{GaP})_x(\text{ZnS})_{1-x}$ solid solutions at temperatures $300 \leq T \leq 1000$ K, based on the multi-configurational supercell approach. GaP has an indirect energy band gap of 2.24 eV while ZnS has a direct energy band gap at Γ of 3.54 eV, and previous computational studies have suggested that mixed GaP–ZnS compounds could be suitable for efficient absorption and emission of visible light.^[10] Indeed, $(\text{GaP})_x(\text{ZnS})_{1-x}$ solid solutions have been experimentally studied in bulk^[21,22] and as nanowires,^[23] showing great promise as optoelectronic materials with band gap tunability and enhanced photoluminescence intensity. Bulk GaP and ZnS present two common polymorphs, zinc-blende and wurtzite (see **Figure 1**), and in the case of $(\text{GaP})_x(\text{ZnS})_{1-x}$ nanowires a strong competition between the two phases has been reported.^[23] For this reason, we consider here both the zinc-blende and wurtzite polymorphs, which generally are observed in binary-octet semiconductors.^[24] Our first-principles results show overall excellent agreement with the experimentally reported structural and electronic properties of GaP–ZnS solid solutions.^[21,22] Interestingly, we predict that compositions $x \approx 25\%$, 50% , and 75% render promising photocatalyst materials for the production of hydrogen fuel from water splitting under visible light, able to meet the requirements of 1) a direct energy gap in the range of

2–3 eV, 2) a valence band level relative to vacuum lying below the water oxidation potential of -5.6 eV, and 3) a conduction band level relative to vacuum lying above the hydrogen reduction potential of -4.4 eV. The solid-solution simulation approach presented in this study, therefore, is very promising for the design and analysis of effective photocatalytic materials, which are pressingly needed for advancing the field of solar-energy storage.

2. Experimental Section

2.1. Density Functional Theory Calculations

We use the generalized gradient approximation to density functional theory (DFT) proposed by Perdew, Burke, and Ernzerhof (PBE)^[25] as implemented in the VASP software package.^[26] The projector augmented wave method is employed to represent the ionic cores,^[27] considering the following electrons as valence states: Ga's 4s and 4p; P's 3s and 3p; Zn's 3d and 4s; and S's 3s and 3p. Wave functions are represented in a plane-wave basis truncated at 500 eV. For integrations within the Brillouin zone (BZ), we employ Monkhorst–Pack k -point grids with a density equivalent to $14 \times 14 \times 14$ in the unit cell. By using these parameters, we obtain zero-temperature energies converged to within 0.5 meV per formula unit AB . Geometry relaxations are performed by using a conjugate-gradient algorithm that allows for cell volume and shape variations; the geometry relaxations are halted after the forces on the atoms fall below $0.01 \text{ eV} \cdot \text{\AA}^{-1}$. In order to reproduce site-occupancy disorder, we adopt a 16-atom simulation cell constructed by replicating $2 \times 2 \times 2$ ($2 \times 2 \times 1$) times the elemental two-atom (four-atom) zinc-blende (wurtzite) unit cell (see next section).

We employ the hybrid HSE06 functional^[28] to estimate the electronic properties of equilibrium configurations previously generated with the PBE functional (see Supporting Information). This two-step approach of using PBE for the generation of the configurational space, followed by HSE06 for electronic properties calculations, is required due to the high computational cost of hybrid functionals. The calculation of phonon frequencies is performed with the small displacement method,^[29] in which the force-constant matrix is calculated in real-space by considering the proportionality between atomic displacements and forces^[30] (see Supporting Information and Figure S1, Supporting Information). In order to estimate the positions relative to vacuum of the valence and conduction bands in $(\text{GaP})_x(\text{ZnS})_{1-x}$ solid solutions, we employ the CRYSTAL09 code^[31] and the hybrid B3PW functional^[32] (see Supporting Information).

2.2. Multi-Configurational Supercell Analysis

The mixing thermodynamics of a site disordered system with a constant number of atoms and at fixed temperature can be described as follows. For a complete set of possible system configurations ($n = 1, \dots, N$), a T -dependent Boltzmann-like occurrence probability p_n can be assigned to each

$$p_n = \frac{\exp(-E_n/k_B T)}{Z_{\text{conf}}} \quad (1)$$

where E_n is the corresponding energy, k_B the Boltzmann constant, and Z the partition function defined as

$$Z_{\text{conf}} = \sum_{n=1}^N \exp(-E_n/k_B T) \quad (2)$$

Accordingly, the Helmholtz free energy of the system F per formula unit (f.u.) can be estimated as

$$F_{\text{conf}} = -\frac{1}{N_{\text{f.u.}}} k_B T \ln Z_{\text{conf}} \quad (3)$$

where $N_{\text{f.u.}}$ is the number of formula units in the simulation cell (equal to the total number of atoms divided by two). The average value of the energy (or of any other well-defined quantity A for each configuration n) in the corresponding configurational space adopts the form

$$\langle E \rangle = \sum_{n=1}^N p_n E_n \quad \left(\langle A \rangle = \sum_{n=1}^N p_n A_n \right) \quad (4)$$

In practice, the configurational space of a chemically disordered solid may comprise a huge number of configurations ($N \gg 10^3$), hence normally it cannot be described with first-principles methods. An effective way to overcome such a limitation is to reduce the total number of possible configurations to $M \ll N$ by exploiting the symmetry properties of the parent crystal phase.^[19] In the generated reduced configurational space, each inequivalent configuration m has an associated degeneracy Ω_m , equal to the number of symmetrically equivalent configurations with same energy E_m , which all together fulfill the relation $N = \sum_{m=1}^M \Omega_m$. The average value of the energy (or of any other well-defined quantity A for each configuration n) in the reduced configurational space then is expressed as

$$\langle E \rangle = \sum_{m=1}^M \tilde{p}_m E_m \quad \left(\langle A \rangle = \sum_{m=1}^M \tilde{p}_m A_m \right) \quad (5)$$

where

$$\tilde{p}_m = \frac{1}{Z_{\text{conf}}} \Omega_m \exp(-E_m/k_B T) \quad (6)$$

The Helmholtz free-energy function in Equation (3) accounts for configurational effects, but neglects contributions from T -induced lattice excitations, which a priori may be important in solid solutions.^[33] To include vibrational contributions in our free-energy calculations, we adopt the expression

$$F = F_{\text{conf}} + F_{\text{vib}} \quad (7)$$

where^[34–36]

$$F_{\text{vib}}(T) = \frac{1}{N_{\text{f.u.}} N_q} k_B T \times \sum_{q^s} \ln \left[2 \sinh \left(\frac{\hbar \omega_{q^s}}{2k_B T} \right) \right] \quad (8)$$

In Equation (8), N_q represents the total number of wave vectors used for integration within the BZ, ω_{q^s} the vibrational eigenfrequencies of the system, and the summation runs over all wave vectors \mathbf{q} and phonon branches s . Due to the huge computational expense associated with first-principles estimation of phonon excitations for a large number of configurations, we calculate F_{vib} just for the structure rendering the highest \tilde{p}_m probability at room temperature (see Equation (6)). We justify this choice in detail later when discussing our results; nevertheless, we estimate that the F_{vib} errors resulting from this procedure are within 10 meV per formula unit (see Supporting Information).

To assess the mixing stability of bulk GaP–ZnS solid solutions, and since we consider zero-pressure conditions in this work, we estimate the corresponding mixing free-energy ΔF as a function of temperature and composition

$$\Delta F(x, T) = F^{\text{ss}}(x, T) - xF^{\text{GaP}}(T) - (1-x)F^{\text{ZnS}}(T) \quad (9)$$

where the superscripts indicate the system for which the Helmholtz free energy is calculated (“ss” stands for solid solution). A disordered system is thermodynamically stable against decomposition into GaP- and ZnS-rich regions if $\Delta F(x, T) < 0$ (although it may be unstable with respect to fluctuations in composition if $\frac{\partial^2 \Delta F(x, T)}{\partial x^2} < 0$); otherwise, the system may be thermodynamically metastable or unstable (depending on whether $\frac{\partial^2 \Delta F(x, T)}{\partial x^2}$ is positive or negative). In this work, we perform the multi-configurational supercell calculations and accompanying statistical analysis with the SOD software.^[19] We use a 16-atom supercell that allows explicit simulation of $(\text{GaP})_x(\text{ZnS})_{1-x}$ solid solutions at nine different compositions (namely, $x_k = \frac{k}{8}$ with $k = 0, \dots, 8$); results at other intermediate compositions are obtained via smooth spline interpolations. The resulting finite-size ΔF bias is estimated to be of the order of 10 meV per formula unit (see tests performed for a larger supercell containing 24 atoms explained in the Supporting Information).

Finally, we note that in the limit of very high temperatures, the configurational entropy S_{conf} equals $\frac{1}{N_{\text{f.u.}}} k_B \ln N$. Due to the finite size of the employed simulation cell, such a configurational entropy limit generally underestimates (in absolute value) the quantity

$$S_{\text{conf}}^{\infty} = -2k_B (x \ln x + (1-x) \ln(1-x)) \quad (10)$$

which is exact in the thermodynamic limit ($N \rightarrow \infty$ at constant composition x) and $T \rightarrow \infty$ (the factor “2” in the formula above appears due to occupancy disorder in both the anion and cation sublattices). Aimed at correcting for such unavoidable finite-size bias, and as has been done in previous work,^[20,37] we apply the following shift to the configurational free energy

$$F_{\text{conf}}^{\text{corr}} = F_{\text{conf}} - T \left(S_{\text{conf}}^{\infty} - \frac{1}{N_{\text{f.u.}}} k_B \ln N \right) \quad (11)$$

By doing this, the correct expression of the configurational free energy is consistently recovered in the $T \rightarrow \infty$ limit. We note that, while this correction is quantitatively significant, the main conclusions presented in the following sections are not qualitatively affected by it (see **Figure 2** and Figure S2, Supporting Information).

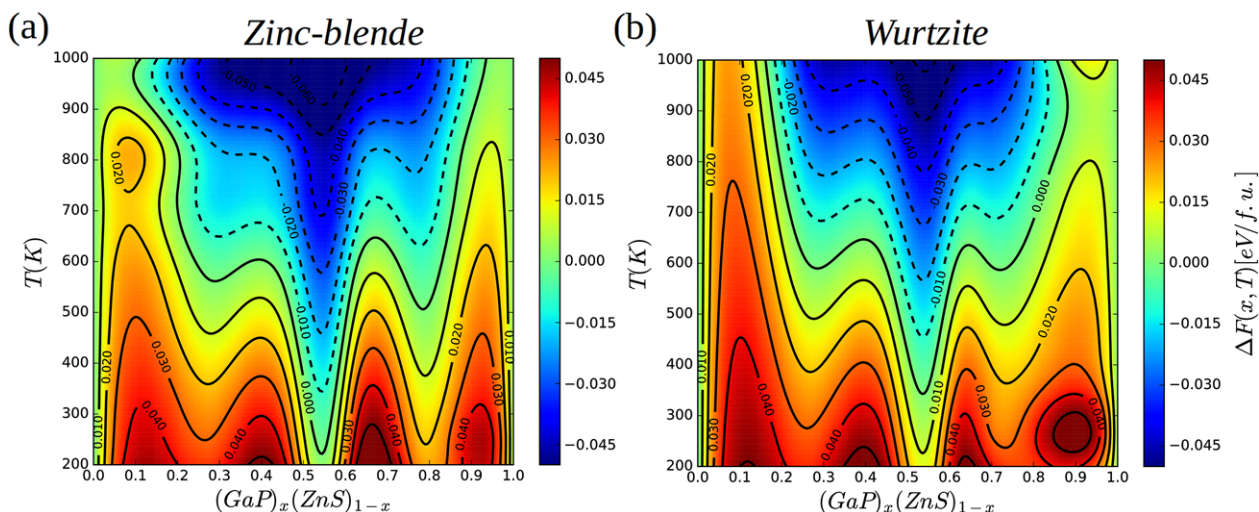


Figure 2. Mixing free-energy of $(\text{GaP})_x(\text{ZnS})_{1-x}$ solid solutions as a function of temperature and composition. a) Zinc-blende and b) wurtzite structures. Solid lines represent iso-value ΔF contours expressed in units of eV per formula unit. Typical ΔF errors are estimated to be of the order of 10 meV per formula unit.

3. Results and Discussion

3.1. Mixing Thermodynamics

Figure 2 shows the mixing free-energy of GaP–ZnS solid solutions calculated as a function of structure, composition, and temperature at zero-pressure conditions (thermal expansion effects have been neglected). We have selected the temperature interval $200 \leq T \leq 1000$ K because typical synthesis temperatures of semiconductor-based solid solutions are of the order of 10^2 – 10^3 K.

Below ambient conditions, we find that all zinc-blende bulk systems are thermodynamically unstable against decomposition into the end-members GaP and ZnS since $\Delta F > 0$, although some compositions may be kinetically stable where $\frac{\partial^2 \Delta F(x, T)}{\partial x^2}$ is locally positive (Figure 2a). However, at temperatures moderately above $T = 300$ K, some disordered crystals with compositions close to $x = 50\%$ become thermodynamically stable against decomposition into end-members GaP and ZnS, since $\Delta F < 0$. The composition range of this stability increases with increasing temperature, reaching $15 \leq x \leq 85\%$ at 1000 K. Therefore, there exists the possibility of generating metastable solid solutions in that range of compositions at ambient temperature via quenching.^[38] The most favorable compositions for the realization of such metastable states are for x close to 25%, 50%, and 75% since at a fixed temperature they render local minima in compositional space (hence $\frac{\partial^2 \Delta F(x, T)}{\partial x^2}$ is negative, so decomposition into GaP- and ZnS-rich regions can be kinetically hindered since small fluctuations in composition result in an increase in free energy). On the contrary, compositions near $x \approx 15\%$, 35%, 65%, and 85% appear to be thermodynamically most unstable (since they render local maxima in compositional space, where $\frac{\partial^2 \Delta F(x, T)}{\partial x^2}$ is positive, and hence small fluctuations in composition result in a decrease in free energy).

The mixing properties of GaP–ZnS solid solutions in the wurtzite structure are very similar to those just described for

the zinc-blende polymorph (Figure 2b). The same most favorable and most disadvantageous compositions for the synthesis of metastable systems are found, and at low temperatures the two corresponding ΔF maps are practically identical. However, as temperature is increased, the mixing free-energy of the zinc-blende phase becomes slightly more favorable than that of the wurtzite polymorph. For instance, at $T = 1000$ K and $x = 50\%$, we estimate $\Delta F = -0.058$ eV per f.u. in the wurtzite phase and -0.065 eV per f.u. in the zinc-blende phase.

To understand the origins of the mixing stability differences between the zinc-blende and wurtzite polymorphs, we plot in **Figure 3** the corresponding ΔF curves calculated at $T = 300$ and 1000 K, split into different contributions (i.e., total, vibrational, and configurational). At room temperature (see Figures 3a,b), the vibrational contribution to the mixing free-energy is practically negligible in both phases (see green lines therein), hence configurational effects are the dominant cause of the ΔF variations observed across the composition series. However, at high temperatures, the vibrational mixing free-energy has a stabilizing effect in both phases, especially at compositions $x > 50\%$, and is largest in absolute value in the zinc-blende polymorph (see Figures 3c,d). For instance, at $T = 1000$ K and $x \approx 60\%$, ΔF_{vib} amounts to -10 meV per f.u. in the zinc-blende phase and to -4 meV per f.u. in the wurtzite phase. The reason for such a vibrational mixing free-energy difference is that the high-frequency phonons, which are dominant at high temperatures, present lower energies in the zinc-blende phase (see Figure S1, Supporting Information). Meanwhile, configurational effects (blue lines in the figures) also tend to favor slightly the cubic polymorph over the hexagonal (e.g., at $T = 300$ K and $x \approx 60\%$ $\Delta F_{\text{conf}} = 30$ meV per f.u. in the zinc-blende phase and 40 meV per f.u. in the wurtzite phase).

Figure 4 shows the free-energy difference between GaP–ZnS solid solutions in the wurtzite and zinc-blende phases expressed as a function of composition at $T = 300$ K. It is appreciated that the zinc-blende polymorph is energetically more favorable than the wurtzite phase at all compositions. Equivalent results

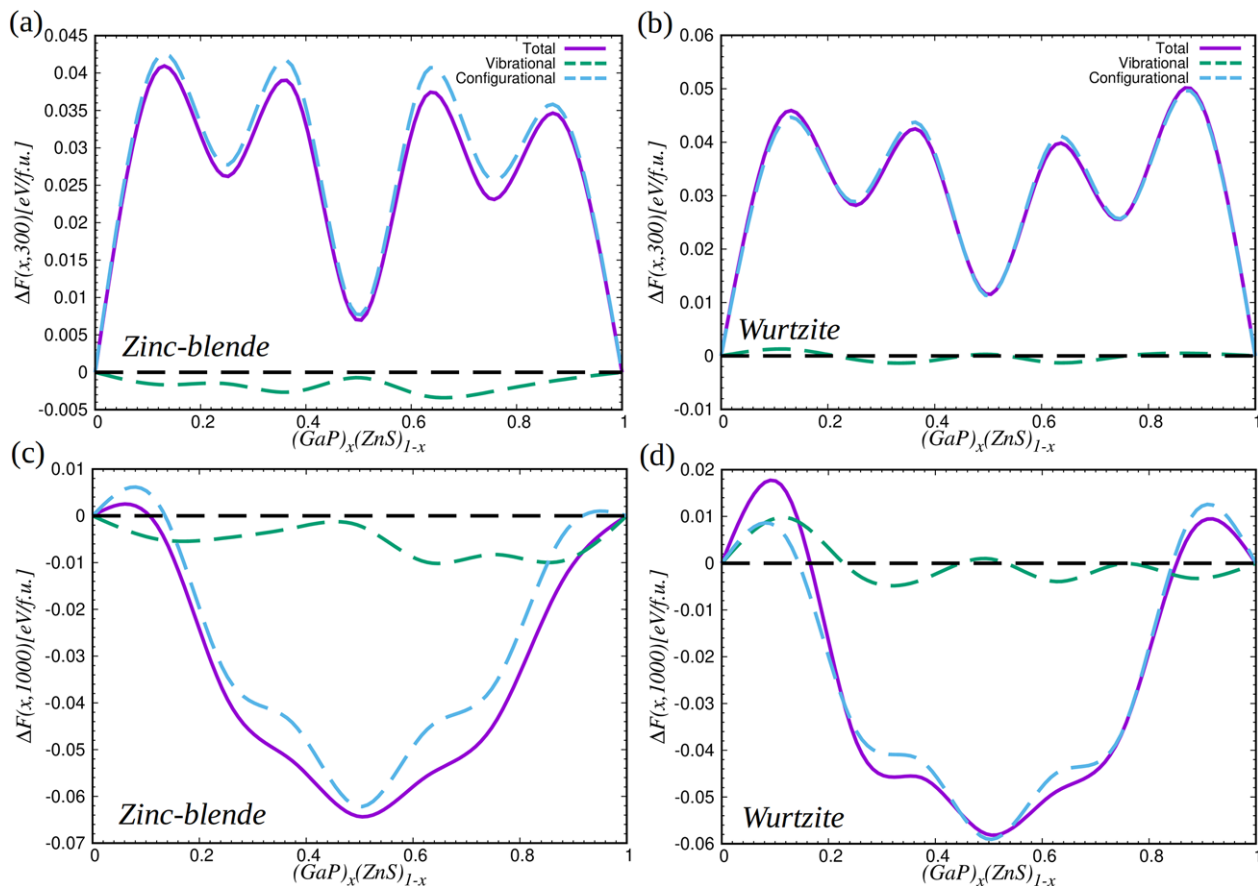


Figure 3. Mixing free-energy of $(\text{GaP})_x(\text{ZnS})_{1-x}$ solid solutions at 300 and 1000 K. a–c) Zinc-blende and b–d) wurtzite structures. Vibrational and configurational (i.e., total minus vibrational) contributions to the total mixing free-energy of the system are expressed as a function of composition. Typical ΔF errors are estimated to be of the order of 10 meV per formula unit.

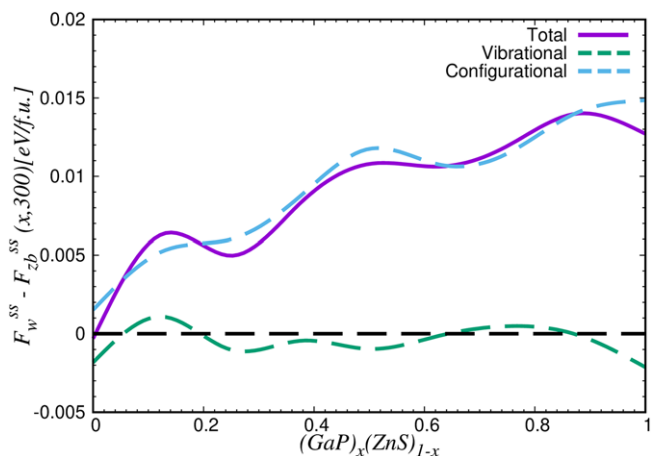


Figure 4. Free-energy difference between the two polymorphs for $(\text{GaP})_x(\text{ZnS})_{1-x}$ solid solutions at $T = 300$ K. Zinc-blende and wurtzite phases are represented as “zb” and “w”, respectively. Configurational and vibrational contributions to the total free-energy difference are indicated. Note that for the end-members F_{conf} reduces to the static energy (see Equations (2) and (3)).

are obtained also at higher temperatures (see Figure S3, Supporting Information). The main reason for the preference of the zinc-blende phase is that the configurational free energy is larger in absolute value than in the hexagonal polymorph. This is clearly appreciated in Figure 4, where we show that the vibrational free-energy differences between the two polymorphs are practically negligible as compared to the configurational counterparts (see blue and green lines therein). Hence our results indicate that the zinc-blende phase is more likely to be synthesized in practice than the wurtzite polymorph, which is consistent with the experimental observations.^[21,22] In the remainder of the article, we will focus on zinc-blende solid solutions at compositions $x = 25\%$, 50% , and 75% since these render the best thermodynamic stabilities.

3.2. Electronic Properties

3.2.1. Energy Band Gap

In Figure 5, we show the normalized energy band gap histograms calculated with the HSE06 hybrid functional^[28] for zinc-blende solid solutions (Supporting Information). Specifically, $E_{\text{gap}}^{\text{HSE06}}$ is

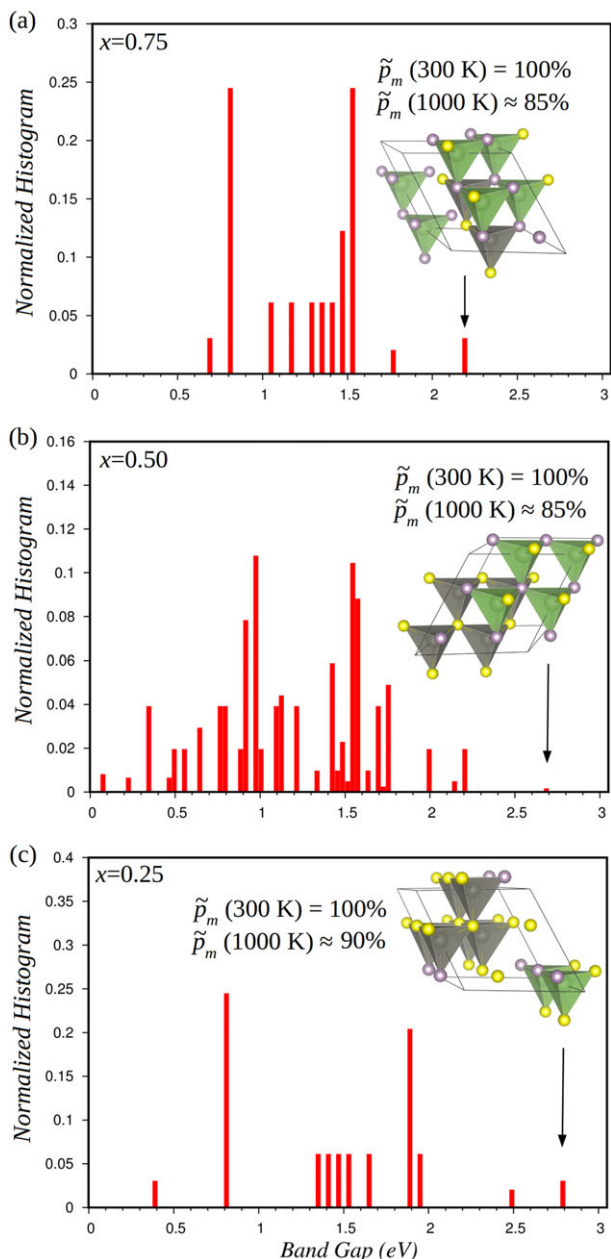


Figure 5. Normalized E_{gap} histogram for zinc-blende $(\text{GaP})_x(\text{ZnS})_{1-x}$ solid solutions. a) $x = 75\%$, b) 50% , and c) 25% compositions. The histogram is constructed by dividing the number of structures within each specific band gap energy interval by the total number of structures. The inequivalent configuration that is most probable in each case is sketched along with its occurrence probability and energy band gap (black arrow). Ga and Zn atoms are represented with green and black spheres and P and S atoms with purple and yellow spheres, respectively. Energy band gaps are estimated with the HSE06 hybrid functional.^[28]

computed for each structure in the corresponding x configurational ensemble and a normalized histogram is constructed subsequently by considering small energy increments (i.e., the number of structures within each specific band gap energy range is divided by the total number of structures—the occurrence prob-

abilities \tilde{p}_m are not considered here). A large dispersion of energy band gap values spanning over the interval $0.50 \lesssim E_{\text{gap}}^{\text{HSE06}} \lesssim 2.75$ eV is observed. In the $x = 50\%$ case (Figures 5b), we find particularly small $E_{\text{gap}}^{\text{HSE06}}$ values, that is, below 0.50 eV, and the normalized histograms are quasi-continuous owing to the higher degree of site-occupancy disorder. It is worth noting that all the calculated energy band gaps are smaller than that of pure ZnS (i.e., $E_{\text{gap}}^{\text{exp}} = 3.5$ eV^[39] and $E_{\text{gap}}^{\text{HSE06}} = 3.1$ eV) and lie within the range of visible or infrared light. Analogous $E_{\text{gap}}^{\text{HSE06}}$ results are obtained also for the wurtzite polymorph (see Figure S4, Supporting Information).

The large dispersions shown in Figure 5 indicate a strong dependence of the energy band gap, and in general of the electronic band structures of $(\text{GaP})_x(\text{ZnS})_{1-x}$ solid solutions, on the local atomic environment. Similar behavior is likely to occur in analogous binary octet semiconductors. For the zinc-blende $(\text{GaP})_{0.5}(\text{ZnS})_{0.5}$ system, we have performed a detailed analysis of the density of electronic states considering different atomic arrangements to better understand the origins of the E_{gap} variations. A clear electronic-structural correlation emerges from our calculations: the larger (smaller) the number of Zn–S bonds, or Ga–P bonds, the larger (smaller) the energy band gap. In turn, the electrostatic potential produced by local environments can be directly related to the number of Zn–S, or Ga–P, bonds. Specifically, when the number of Zn–S bonds, or Ga–P bonds, is minimized (leading to the smallest E_{gap}) the electrostatic potential at the S and P atoms forming the top of the valence band (see Figure S5, Supporting Information) is lowest (i.e., their atomic environment is most negatively charged), hence the energy of the valence band is high. Likewise, the electrostatic potential at the Ga atoms forming the bottom of the conduction band (see Figure S5, Supporting Information) is highest when the number of Ga–P bonds, or Zn–S bonds, is minimized, which induces a lowering of the energy of the conduction band.

Remarkably, however, when the average value of E_{gap} is calculated with the multi-configurational supercell approach (see Equations (5) and (6) in Section 2.2), the band gap dispersions shown in Figure 5 play just a marginal role. As we explain next, this is due to the fact that one particular configuration is much more likely to occur than the rest (see the occurrence probabilities indicated in Figure 5 and the full \tilde{p}_m spectra shown in Figure S6, Supporting Information).

Figure 6 shows the T -dependent average value of the energy band gap calculated with the multi-configurational supercell method (see Equations (5) and (6)) for GaP–ZnS solid solutions at $x = 25\%$, 50% , and 75% . E_{gap} presents an almost constant value throughout the whole temperature interval $300 \leq T \leq 1000$ K at any composition, and increases from 2.1 to 2.8 eV as x decreases from 75 to 25%. As could have been foreseen, the energy band gap of the mixed compound is larger when the content of ZnS is larger (recall that $E_{\text{gap}}^{\text{exp}} = 2.3$ and 3.5 eV in pure GaP and ZnS,^[10,39] respectively). The reason for the steady behavior of E_{gap} as a function of temperature is that in all the analyzed cases, the spectra of occurrence probabilities \tilde{p}_m (see Equation (6)) very much favor the configuration with lowest energy (and low configurational degeneracy as shown by the histograms in Figure 5) over the others (Figure S6, Supporting Information). The lowest-energy configurations determined at each x are

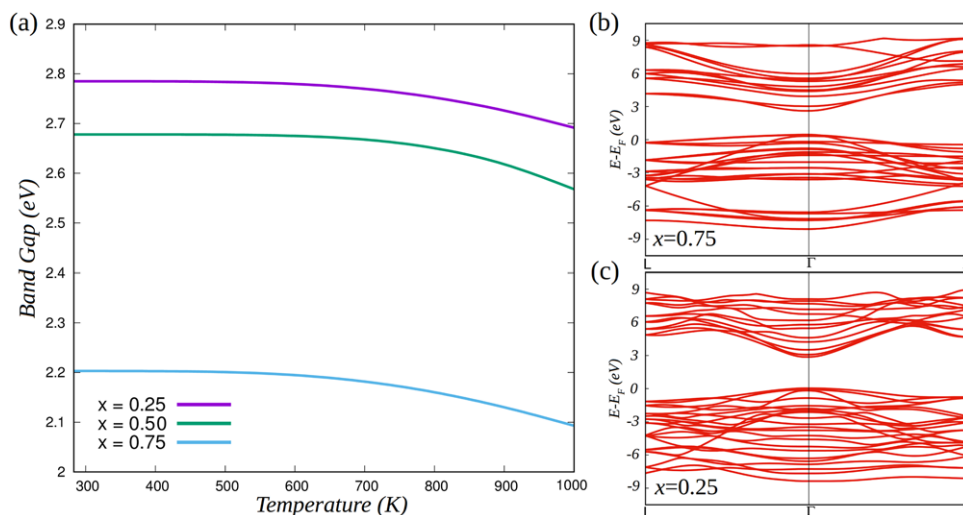


Figure 6. Electronic band structure of zinc-blende $(\text{GaP})_x(\text{ZnS})_{1-x}$ solid solutions. a) Averaged energy band gap as a function of temperature and composition calculated with the multi-configurational supercell method. b) Electronic band structure calculated for the most probable configuration at $x = 75\%$, which renders a direct energy band gap at Γ . c) Idem at $x = 25\%$. Energy band gaps are estimated with the exchange-correlation HSE06 hybrid functional.^[28]

sketched in Figure 5, along with their energy band gaps (see black arrows therein). As can be observed, the lowest-energy configurations render structures in which the number of Zn–S, or Ga–P, bonds are maximized, which as we have explained before correlates directly to largest energy band gaps.

The small E_{gap} variations observed in Figure 6a at $T > 600$ K stem from the increasingly more important role that highly degenerate configurations (i.e., with large Ω_m 's, see Section 2.2) start to play at high temperatures (Figure S6, Supporting Information). Analogous energy band gap results are obtained also for the wurtzite phase (see Figure S7, Supporting Information). It is worth noting that the highly peaked nature of the \tilde{p}_m distributions calculated in GaP–ZnS solid solutions (see Figure S6, Supporting Information) comes to justify the strategy that we have followed for estimating vibrational contributions to the mixing free-energy (see Section 2.2).

The energy band gap results shown in Figure 6 are in very good agreement with the optical measurements performed by Shintani and Sonomura more than 40 years ago.^[21,22] In particular, the room-temperature experimental results $E_{\text{gap}}^{\text{exp}} = 2.4$ – 2.6 , 2.4 – 2.5 , and 2.2 – 2.4 eV obtained at $x = 25\%$, 50% , and 75% , respectively, compare very well to our theoretical values $E_{\text{gap}}^{\text{HSE06}} = 2.80$, 2.65 , and 2.20 eV. Moreover, in our simulations, we find that all compositions $x \leq 75\%$ render direct energy band gaps at Γ (see Figure 6b,c, obtained for the most probable configurations), which also is consistent with the reported experimental observations.^[21,22] Thus, we confirm that zinc-blende $(\text{GaP})_x(\text{ZnS})_{1-x}$ solid solutions display promising visible-light absorption features, namely, direct energy band gaps lying in the range 2 – 3 eV^[10] (likewise, the wurtzite polymorph possesses also promising electronic properties, see Figure S7, Supporting Information). Overall, our theoretical findings demonstrate that the present computational approach, which is based on the multi-configurational supercell method and density functional theory calculations, is able to reproduce closely the electronic band structure features of complex materials with site-occupancy disorder.

3.2.2. Energy Band Levels Relative to Vacuum

Promising photocatalytic materials should present not only suitable energy band gaps but also adequate energy band levels relative to vacuum.^[40] Here, we are interested in assessing the potential of $(\text{GaP})_x(\text{ZnS})_{1-x}$ solid solutions for production of hydrogen fuel from water splitting under visible light. To this end, we calculated the position of the top of the valence band (VB) and bottom of the conduction band (CB) relative to the vacuum energy using the CRYSTAL09 code^[31] with the methods described in Section 2.1 and Supporting Information at compositions $x = 0\%$, 25% , 50% , 75% , and 100% . In particular, we calculated the difference between the energy of the $1s$ orbitals in bulk GaP and bulk ZnS and in the center of ZnS and GaP slabs, ΔE_{1s} . A non-polar (110)-oriented slab with a total thickness equivalent to 20 atomic layers was used for these calculations (corresponding to a thickness of 37 Å for ZnS and of 38 Å for GaP; such a length provides sufficiently well-converged results). The (110) surface was selected because this has been reported to be the most stable for zinc-blende ZnS^[41,42] and GaP.^[43] The cell length in the direction perpendicular to the slab surface was set to 500 Å, giving a large enough vacuum gap to prevent interactions between periodic images of the slab. The slab was fully relaxed in all cases. The energy difference ΔE_{1s} was then added to the VB and CB energies in order to obtain the energies relative to vacuum. For the solid solutions, the shift applied to the band energies was a weighted average of those for pure ZnS and pure GaP. This method has been previously applied to GaN–ZnO solid solutions.^[9]

Figure 7 shows our hybrid B3PW^[32] results for the energy band levels relative to vacuum for different compositions. We reiterate that an ideal hydrogen photocatalyst material should present 1) a direct energy band gap lying in the range 2 – 3 eV, 2) a VB level relative to vacuum lying below the water oxidation potential of -5.6 eV, and 3) a CB level relative to vacuum lying above the hydrogen reduction potential of -4.4 eV. First, we note that our band alignment results obtained for bulk GaP and ZnS are

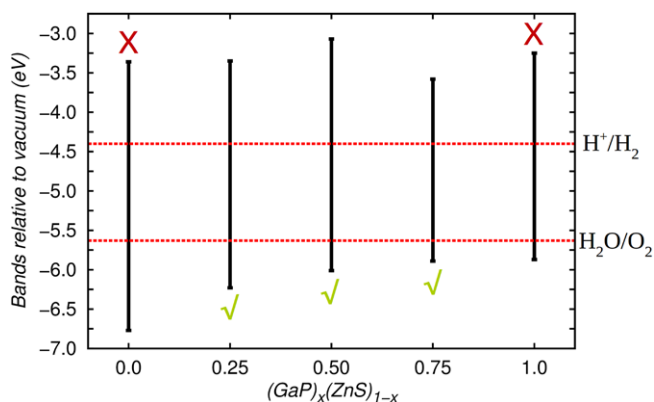


Figure 7. Energy bands relative to the vacuum level in zinc-blende $(\text{GaP})_x(\text{ZnS})_{1-x}$ solid solutions. Γ energy band gaps are direct for compositions $x = 0\%$, 25% , 50% , and 75% . All energy band gaps lie within the $2\text{--}3\text{ eV}$ interval except for ZnS. The redox potentials relative to the vacuum level for the hydrogen reduction and water oxidation reactions are indicated with dashed lines. Energy band gaps and levels are estimated with the B3PW hybrid functional^[32] and CRYSTAL09 code.^[31]

in good agreement with previous first-principles calculations reported by other authors.^[44] Pure GaP and ZnS are not suitable for photocatalytic water splitting since they do not fulfill condition (1) above. In contrast, all three solid solutions $x = 25\%$, 50% , and 75% fulfill requirements (1)–(3) and hence are promising hydrogen photocatalyst materials for water splitting. For instance, in the $x = 75\%$ ($x = 25\%$) case the VB level lies 0.3 (0.6) eV below -5.6 eV and the CB level is 0.8 (1.0) eV above -4.4 eV. We note that metastable ZnS-rich solid solutions, namely, cases $x = 25$ and 50% , are of particular interest in terms of practical applications since GaP is scarce in nature and thus expensive, while ZnS is earth-abundant.

4. Summary

We have presented a comprehensive first-principles study of the mixing thermodynamics, and structural, electronic, and photocatalytic properties of $(\text{GaP})_x(\text{ZnS})_{1-x}$ solid-solutions as a function of temperature and composition. Our theoretical approach relies on the multi-configurational supercell method, which allows a rigorous statistical treatment of site-occupancy disorder as well as the calculation of accurate thermodynamic and functional properties of solid solutions. Valuable physical insights into the atomistic mechanisms behind the thermodynamic and functional features of solid solutions are attained on-the-go and interpreted easily in terms of probabilities (e.g., Boltzmann-like occurrence factors).

We find overall excellent agreement between our calculations and the experimental data reported on the structural and electronic properties of GaP–ZnS solid solutions. This good accordance demonstrates the accuracy and reliability of our employed computational method. Based on our energy band gap and band alignment results, we predict that compounds $x = 25\%$, 50% , and 75% are very promising as photocatalyst materials for the generation of hydrogen from water splitting under visible light. Similar theoretical studies to ours may be conducted for other en-

couraging combinations of semiconductor materials (e.g., GaN–ZnO and CdS–ZnS). Our theoretical approach is computationally affordable and fully general, hence it has the potential to accelerate the development of optimized materials based on semiconductor solid solutions for solar-energy storage; also, to improve the design of materials for a range of other applications in which tuning of the opto-electronic behavior is important. We envisage that our approach will promote and assist the experimental synthesis of bettered photocatalysts by providing useful insights into their mixing thermodynamics.

Supporting Information

Supporting Information is available from the Wiley Online Library or from the author.

Acknowledgements

This research was supported under the Australian Research Council's Future Fellowship funding scheme (No. FT140100135). Computational resources and technical assistance were provided by the Australian Government and the Government of Western Australia through the National Computational Infrastructure (NCI) and Magnus under the National Computational Merit Allocation Scheme and The Pawsey Supercomputing Centre.

Conflict of Interest

The authors declare no conflict of interest.

Keywords

density functional theory calculations, multiconfigurational supercell approach, photocatalytic materials, semiconductor solid solutions

Received: October 1, 2018

Revised: October 21, 2018

Published online:

- [1] A. Kudo, Y. Miseki, *Chem. Soc. Rev.* **2009**, *38*, 253.
- [2] F. E. Osterloh, *Chem. Mater.* **2008**, *20*, 35.
- [3] H. Tong, S. Ouyang, Y. Bi, N. Umezawa, M. Oshikiri, J. Ye, *Adv. Mater.* **2012**, *24*, 229.
- [4] C. Xing, Y. Zhang, W. Yan, L. Guo, *Int. J. Hydrog. Energy* **2006**, *31*, 2018.
- [5] K. Maeda, K. Teramura, D. Lu, T. Takata, N. Saito, Y. Inoue, K. Domen, *Nature* **2006**, *440*, 295.
- [6] Z. G. Yi, J. H. Ye, *Appl. Phys. Lett.* **2007**, *91*, 254108.
- [7] Z. Zou, J. Ye, K. Sayama, H. Arakawa, *Nature* **2001**, *414*, 625.
- [8] L. L. Jensen, J. T. Muckerman, M. D. Newton, *J. Phys. Chem. C* **2008**, *112*, 3439.
- [9] C. Di Valentin, *J. Phys. Chem. C* **2010**, *114*, 7054.
- [10] J. N. Hart, N. L. Allan, *Adv. Mater.* **2013**, *25*, 2989.
- [11] J. González-López, S. E. Ruiz-Hernández, A. Fernández-González, A. Jiménez, N. H. de Leeuw, R. Grau-Crespo, *Geochim. Cosmochim. Acta* **2014**, *142*, 205.
- [12] O. Diéguez, J. Íñiguez, *Phys. Rev. Lett.* **2011**, *107*, 057601.

- [13] Y. E. Licea, R. Grau-Crespo, L. A. Palacio, A. C. Faro, Jr., *Catal. Today* **2017**, 292, 84.
- [14] C. Cazorla, A. K. Sagotha, M. King, D. Errandonea, *J. Phys. Chem. C* **2018**, 122, 1267.
- [15] L. Bellaiche, D. Vanderbilt, *Phys. Rev. B* **2000**, 61, 7877.
- [16] I. T. Todorov, N. L. Allan, M. Y. Lavrentiev, C. Freeman, C. E. Mohn, J. A. Purton, *J. Phys.: Condens. Matter* **2004**, 16, S2751.
- [17] N. L. Allan, G. D. Barrera, R. M. Fracchia, M. Yu. Lavrentiev, M. B. Taylor, I. T. Todorov, J. A. Purton, *Phys. Rev. B* **2001**, 63, 094203.
- [18] S.-H. Wei, L. G. Ferreira, J. E. Bernard, A. Zunger, *Phys. Rev. B* **1990**, 42, 9622.
- [19] R. Grau-Crespo, S. Hamad, C. R. A. Catlow, N. H. de Leeuw, *J. Phys. Condens. Matter* **2007**, 19, 256201.
- [20] R. Grau-Crespo, U. V. Waghmare, *Molecular Modeling for the Design of Novel Performance Chemicals and Materials*, CRC Press, Boca Raton, Florida, United States **2012**, pp. 299–322.
- [21] A. Shintani, S. Minagawa, *J. Phys. Chem. Solids* **1973**, 34, 911.
- [22] H. Sonomura, T. Uragaki, T. Miyauchi, *Jpn. J. Appl. Phys.* **1973**, 12, 968.
- [23] K. Park, J. A. Lee, H. S. Im, C. S. Jung, H. S. Kim, J. Park, C.-H. Lee, *Nano Lett.* **2014**, 14, 5912.
- [24] C.-H. Yeh, Z. W. Lu, S. Froyen, A. Zunger, *Phys. Rev. B* **1992**, 46, 10086.
- [25] J. P. Perdew, K. Burke, M. Ernzerhof, *Phys. Rev. Lett.* **1996**, 77, 3865.
- [26] G. Kresse, J. Fürthmüller, *Phys. Rev. B* **1996**, 54, 11169.
- [27] P. E. Blöchl, *Phys. Rev. B* **1994**, 50, 17953.
- [28] A. V. Krukau, O. A. Vydrov, A. F. Izmaylov, G. E. Scuseria, *J. Chem. Phys.* **2006**, 125, 224106.
- [29] G. Kresse, J. Furthmüller, J. Hafner, *Europhys. Lett.* **1995**, 32, 729.
- [30] D. Alfè, *Comp. Phys. Commun.* **2009**, 180, 2622.
- [31] R. Dovesi, R. Orlando, B. Civalieri, C. Roetti, V. R. Saunders, C. M. Zicovich-Wilson, *Z. Kristallogr.* **2005**, 220, 571.
- [32] A. D. Becke, *J. Chem. Phys.* **1993**, 98, 5648.
- [33] A. van de Walle, G. Ceder, *Rev. Mod. Phys.* **2002**, 74, 11.
- [34] C. Cazorla, O. Diéguez, *J. Íñiguez, Sci. Adv.* **2017**, 3, e1700288.
- [35] C. Cazorla, *J. Íñiguez, Phys. Rev. B* **2013**, 88, 214430.
- [36] C. Cazorla, J. Boronat, *Rev. Mod. Phys.* **2017**, 89, 035003.
- [37] U. Becker, A. Fernandez-Gonzalez, M. Prieto, R. Harrison, A. Putnis, *Phys. Chem. Miner.* **2000**, 27, 291.
- [38] H. Jones, *Rep. Prog. Phys.* **1973**, 36, 1425.
- [39] J. Heyd, J. E. Peralta, G. E. Scuseria, R. L. Martin, *J. Chem. Phys.* **2005**, 123, 174101.
- [40] P. G. Moses, M. Miao, Q. Yan, C. G. Van de Walle, *J. Chem. Phys.* **2011**, 134, 084703.
- [41] S. Hamad, S. Cristol, C. R. A. Catlow, *J. Phys. Chem. B* **2002**, 106, 11002.
- [42] K. Wright, G. W. Watson, S. C. Parker, D. J. Vaughan, *Am. Mineral.* **1998**, 83, 141.
- [43] K. Hayashi, M. Ashizuka, R. C. Bradt, H. Hirano, *Mater. Lett.* **1982**, 1, 116.
- [44] C. G. Van de Walle, J. Neugebauer, *Nature* **2003**, 423, 626.